

ANALYSIS OF FLUCTUATION CONDUCTIVITY IN $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ V.M. ALIEV¹, J.A. RAGIMOV², R.I. SELIM-ZADE¹, B.A. TAIROV¹¹*G.M. Abdullayev Institute of Physics of Azerbaijan NAS**131, H. Javid ave., Baku, AZ 1143**v_aliev@bk.ru*²*Azerbaijan Medical University, 23, Bakikhanov str., Baku, AZ-1022*

The mechanism of formation of excess conductivity in cuprate HTSC $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ and $YBa_2Cu_3O_{7-\delta}$ was considered within the framework of the local pair model taking into account the Aslamazov-Larkin theory near T_c . The temperature T_0 of the transition T_0 from the 2D fluctuation region to the 3D region (the temperature of the 2D-3D crossover) is determined. The coherence lengths of the fluctuation Cooper pairs $\xi_c(0)$ along the c axis are calculated. It was shown that a partial substitution of Y by Cd in the Y-Ba-Cu-O system leads to a decrease in $\xi_c(0)$ by ~ 1.7 times (from 6.32\AA to 3.8\AA), as well as to the expansion as the region of existence pseudogaps and superconducting (SC) fluctuations near T_c . The temperature dependence of the pseudogap $\Delta^*(T)$ and the values of $\Delta^*(T_c)$ are determined, and temperatures T_m corresponding to the maximum temperature dependence of the pseudogap in these materials are estimated. The maximum values of the pseudogap in samples $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ and $YBa_2Cu_3O_{7-\delta}$ are, respectively, 34.56meV and 34.65meV.

Keywords: superconductivity, pseudogap, excess conductivity, coherence length, composition.

PACS: 74.25. Fy, 74.20.Mn, 74.72. ± h, 74.25. ± q, 74.25. Jb

1. INTRODUCTION

In recent years, the group of works [1–5] devoted to the analysis of pseudogap effects in HTSC compounds has appeared. Pseudogap (PG) is a unique phenomenon characteristic of HTSC with an active CuO_2 plane (cuprates) in the doping region less than optimal. It manifests itself in studies of the phenomena of tunneling, photoemission, heat capacity [2, 4] and other properties of HTSC. It is assumed that at a certain temperature $T^* \gg T_c$ (T_c is the critical temperature of the superconducting transition) the density of states on the Fermi surface is redistributed: on a part of this surface the density of states decreases. Below the temperature T^* , the compound is in a pseudogap state. In these works, possible conduction mechanisms in the modes of the normal, superconducting, and pseudogap states in HTSC are also discussed.

Recently, the work [6], devoted to the study of the pseudogap state in $Pb_{0.55}Bi_{1.5}Sr_{1.6}La_{0.4}CuO_{6+\delta}$ (Pb - $Bi2201$) appeared. A series of Pb - $Bi2201$ single crystals was obtained, on which a wide range of investigations were conducted to identify the pseudogap state. The results of studies on three different experimental methods indicate that the appearance of a pseudogap at $T \cong 132\text{K}$ should be perceived only as a phase transition. Thus, the authors confirmed the assumption that at the temperature decreasing, the HESC material must undergo two phase transitions: first the appearance of a pseudogap, and then a transition to the superconducting state.

However, as noted by A. Abrikosov [7], the pseudogap state cannot really be considered as some kind of new phase state of matter, since the PG is not separated from the normal state by a phase transition. So, the question of a possible phase transition at $T=T^*$ also remains open. At the same time, it can be said that a crossover occurs at $T=T^*$ [1]. Below this temperature, due to reasons not yet established to date,

the density of quasiparticle states at the Fermi level begins to decrease. Actually, for this reason, this phenomenon is called "pseudogap". For the first time, this result was obtained in experiments on the study of NMR in a weakly doped Y123 system, in which an anomalous decrease of the Knight shift [2] during cooling, which is directly related to the density of states at the Fermi level in the Landau theory, was observed.

In order to receive answers to the above questions in this work, we have analyzed the excess conductivity separated from resistive measurements on partially doped $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ with a SC transition at 85 K.

Thus, the aim of this work is to study the normal state of $YBa_2Cu_3O_{7-\delta}$ and $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ in the temperature range $T^* > T > T_c$, to determine their physical characteristics, as well as to study the possibility of the occurrence of the PG states in these compounds. The analysis was carried out on the basis of the study of excess conductivity above T_c in the framework of the local pair (LP) model [3,4] taking into account the Aslamazov – Larkin fluctuation theory [8] near T_c .

2. EXPERIMENTAL RESULTS AND THEIR PROCESSING

The method for obtaining $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ is described in [9].

The temperature dependences of the specific resistivity ρ of the samples Y1 and Y2 are showed in fig.1.

The critical temperatures of the SC transition T_c were determined from the maximum obtained by differentiation of the curve $\rho(T)$. Critical temperature of investigated samples is $T_{c1}=92.63\text{K}$ (Y1) and $T_{c2}=90.9\text{K}$ (Y2), respectively (fig.1). In this case, the

resistivity of the sample $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ in the normal phase at 300K increases almost 2 times compared to $YBa_2Cu_3O_{7-\delta}$.

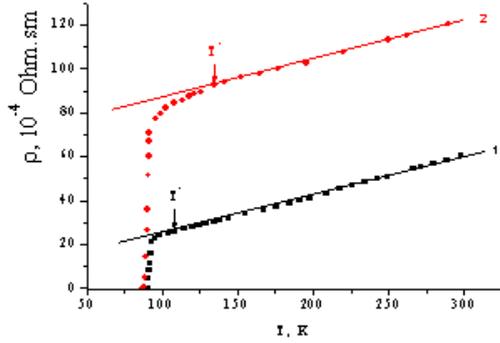


Fig.1. Temperature dependences of the resistivity of samples Y1- $YBa_2Cu_3O_{7-\delta}$ (1) and Y2- $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ (2).

3. FLUCTUATION CONDUCTIVITY

The linear course of the temperature dependence of the specific resistance of samples Y1 and Y2 in the normal phase is well extrapolated by the expressions $\rho_n(T) = (D + \kappa T + BT^2)$ and $\rho_n(T) = (\rho_0 + \kappa T + BT^2)$ (here D , B and k are some constants). This linear relationship, extrapolated to the low temperature range, was used to determine excess conductivity $\Delta\sigma(T)$ according to:

$$\Delta\sigma(T) = \rho^{-1}(T) - \rho_v^{-1}(T) \quad (1)$$

The analysis of the behavior of excess conductivities was carried out in the framework of the local pair model [4, 10].

Assuming the possibility of the formation of local pairs [3,4] in samples at temperatures below $T^* = 107.57$ K (Y1) and $T^* = 140.24$ K (Y2), the experimental results obtained near T_c were analyzed taking into account the occurrence of fluctuation Cooper pairs (FCP) above T_c in the framework of the theory of Aslamazov-Larkin (AL) [8].

The fig. 2 shows dependence of the logarithm of the excess conductivity of the samples Y1 (1) and Y2 (2) on the logarithm of the reduced temperature $\varepsilon = (T / T_c - 1)$.

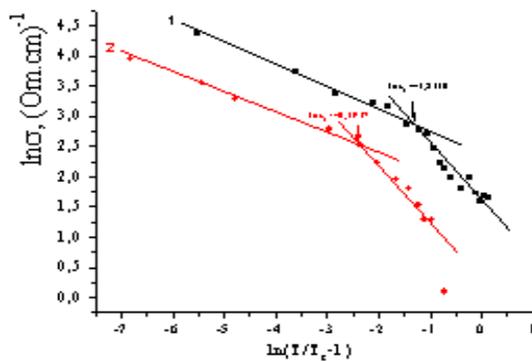


Fig. 2. The dependences of the logarithm of excess conductivity on logarithm $(T / T_c - 1)$ of samples Y1 (1) and Y2 (2).

The solid lines are the calculation in the framework of the Aslamazov-Larkin theory. According to the theory of AL, as well as Hikami – Larkin (HL) developed for HTSC [10], in the region of $T > T_c$ (but near T_c), the fluctuation coupling of charge carriers occurs, leading to the appearance of fluctuation conductivity (FC). In this region, the temperature dependence of excess conductivity on temperature is described by the expressions:

$$\Delta\sigma_{AL3D} = C_{3D} \cdot \{e^2 / [32\hbar\xi_c(0)]\} \varepsilon^{-1/2}, \quad (2)$$

$$\Delta\sigma_{AL2D} = C_{2D} \cdot \{e^2 / [16\hbar d]\} \varepsilon^{-1}, \quad (3)$$

respectively for three-dimensional (3D) and two-dimensional (2D) region. The scaling coefficients C are used to combine the theory with experiment [4].

Thus, by the angle of inclination α of dependences $\ln(\Delta\sigma)$ as a function of $\varepsilon = \ln(T/T_c - 1)$ (see fig. 2), we can distinguish 2D ($tg\alpha = -1$) and 3D ($tg\alpha = -1/2$) regions of phase transition. It can also determine the crossover temperature T_0 (the transition temperature from $\Delta\sigma_{2D}$ to σ_{3D}) and the tangents of the slopes of the dependences $\Delta\sigma(T)$ corresponding to the exponents ε in equations (2) and (3). The corresponding values of the parameters 2D and 3D regions determined from the experiment for sample Y1 are 2D ($tg\alpha = -1.04$) and 3D ($tg\alpha = -0.44$) and for Y2 2D ($tg\alpha = -1.1$) and 3D ($tg\alpha = -0.49$).

On basis of temperature of the crossover T_0 , which corresponds to $\ln\varepsilon_0$, according to fig.2, it can determine the coherence length of local pairs along the “c” axis [11,12]:

$$\xi_c(0) = d\sqrt{\varepsilon_0}, \quad (4)$$

here $d \approx 11.7 \text{ \AA}$ is the distance between the inner conducting planes in Y-Ba-Cu-O [13]. The values of $\xi_c(0) = 6.32 \text{ \AA}$ ($\ln\varepsilon_0 \approx -1.2318$) for Y1 and $\xi_c(0) = 3.535$ ($\ln\varepsilon_0 \approx -2.3937$) for Y2 was obtained, accordingly.

4. ANALYSIS OF THE MAGNITUDE AND TEMPERATURE DEPENDENCE OF THE PSEUDOGAP

As noted above, in the cuprates at $T < T^*$, the density of electron states of quasiparticles on the Fermi level decreases [14] (the cause of this phenomenon is not yet fully elucidated), which creates conditions for the formation of a pseudogap in the excitation spectrum and it leads ultimately to the formation of an excess conductivity. The magnitude and temperature dependence of the pseudogap in the investigated samples was analyzed using the local pair model, taking into account the transition from Bose-Einstein condensation (SCB) to the BCS mode predicted by the theory [10] for HTSC when the temperature decreases in the interval $T^* < T < T_c$. Note that excess conductivity exists precisely in this temperature range, where fermions supposedly form pairs -the so-called strongly coupled bosons (PRS).

The pseudogap is characterized by a certain value of the binding energy $\varepsilon_b \sim 1/\xi^2(T)$, causing the creation of such pairs [10,13], which decreases with temperature, because the coherence length of the Cooper pairs $\xi(T) = \xi(0)/(T/T_c - 1)^{1/2}$, on the contrary, increases with decreasing temperatures. Therefore, according to the LP model, the SCB are transformed into the FCP when the temperature approaches T_c (BEC-BCS transition), which becomes possible due to the extremely small coherence length $\xi(T)$ in cuprates.

From our studies, we can estimate the magnitude and temperature dependence of PG, based on the temperature dependence of excess conductivity in the entire temperature range from T^* to T_c according to [3,13]:

$$\Delta\sigma(\varepsilon) = \left\{ \frac{A(1-T/T^*)[\exp(-\Delta^*/T)]e^2}{16\eta\xi_c(0)\sqrt{2\varepsilon_0^*} \cdot sh(2\varepsilon/\varepsilon_0^*)} \right\} \quad (5)$$

where the $(1 - T/T^*)$ determines the number of pairs formed at $T \leq T^*$; and the $\exp(-\Delta^*/T)$ determines the number of pairs destroyed by thermal fluctuations below the BEC-BCS transition temperature. The coefficient A has the same meaning as the coefficients C3D and C2D in (2) and (3).

The solution of equation (5) gives the value of Δ^* :

$$\Delta^*(T) = T \cdot \ln \left\{ \frac{A(1-T/T^*)e^2}{\Delta\sigma(T)16\eta\xi_c(0)\sqrt{2\varepsilon_0^*} \cdot sh(2\varepsilon/\varepsilon_0^*)} \right\} \quad (6)$$

where $\Delta\sigma(T)$ is the experimentally determined excess conductivity.

Fig. 3 shows the dependence of logarithm of the excess conductivity of samples Y1 and Y2 on the inverse temperature.

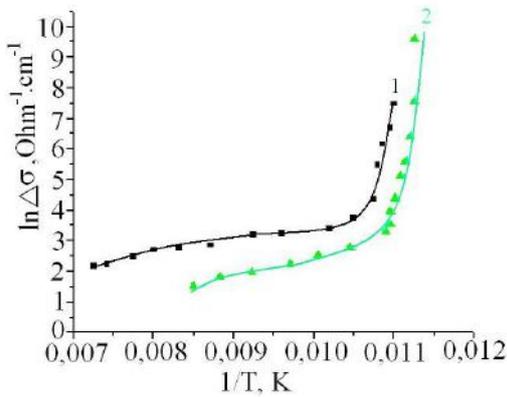


Fig.3. The dependences of logarithm of excess conductivity on inverse temperature: 1-Y1; 2-Y2; solid lines - approximation of equation 3 with the parameters given in text.

The choice of such coordinates is due to the strong sensitivity of the linear region $\ln\Delta\sigma(1/T)$ to the value of $\Delta^*(T_c)$ in equation (5), which allows us to estimate this parameter with high accuracy (this is

necessary to find the coefficient A) [3,13,15]. The dependences $\ln\Delta\sigma(1/T)$ were calculated according to the method approved in [12]. As can be seen from fig. 3 (curves 1 and 2), in this case, the values $\ln\Delta\sigma(1/T)$ calculated for both samples with parameters: $A = 82.4 \pm 0.1$, $T^* = 107.57$ K, $\xi_c(0) = 6.32$ Å (Y1) and $A = 7.6 \pm 0.1$, $T^* = 140.24$ K, $\xi_c(0) = 3.535$ Å (Y2) are in good agreement with the experimental data.

The temperature dependence and the value of the pseudogap parameter $\Delta^*(T)$ (fig. 4) were calculated on the basis of equation (6) with the parameters given above.

As noted in [3,4,13], the value of the coefficient A is selected from the condition of coincidence of the temperature dependence of $\Delta\sigma$ (equation (5), assuming $\Delta^* = \Delta^*(T)$) with experimental data in the region of 3D fluctuations near T_c . According to [13,16] the optimal approximation for the HTSC material is achieved with values of $2\Delta^*(T_c)/\kappa_B T_c \approx 5 \div 7$. For sample Y1, the values $2\Delta^*(T_c)/\kappa_B T_c = 5.4$, and for Y2 $2\Delta^*(T_c)/\kappa_B T_c = 5$ have been obtained. As a result, the values of $A = 82.4$ and $\Delta^*(T_c) = 92.62 \cdot 2.7 = 250.07$ K; for Y2 $A = 7.6$ and $\Delta^*(T_c) = 90.9 \cdot 2.5 = 227.25$ K have been obtained, and it consistent with the experimental data (fig. 4).

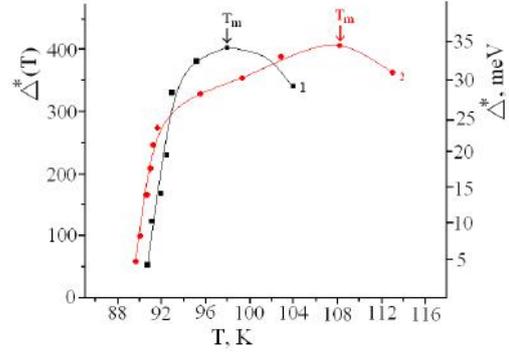


Fig.4. Temperature dependences of the calculated pseudogap of samples Y1 (1) and Y2 (2) with the parameters given in the text. The arrows show the maximum pseudogap values.

The temperature dependences of $\Delta^*(T)$ obtained on the basis of equation (6) are shown in fig. 4. The maximum values of the pseudogap for Y1 $\Delta^*_m \approx 34.56$ meV ($\Delta^*(T_m) \approx 402.66$ K, $T_m = 97.98$ K) for Y2 $\Delta^*_m \approx 34.65$ meV ($\Delta^*(T_m) \approx 406.0$ K, $T_m \approx 108.15$ K) are determined.

From the presented data in fig. 4, it is also seen that as T decreases, the pseudogap value first increases, then, after passing through a maximum, decreases. This decrease is due to the transformation of the SCB in the PCF as a result of the BEC-BCS transition, which accompanied by an increase in excess conductivity at $T \rightarrow T_c$. Such a behavior of Δ^* with decreasing temperature was first found on YBCO films [3.13] with different oxygen contents, which seems to be typical of cuprate HTSC [13]. Thus, it can be concluded that in investigated $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ and $YBa_2Cu_3O_{7-\delta}$ samples, it is possible to formed local pairs of charge carriers at

$T \gg T_c$, which creates conditions for the formation of a pseudogap [13,16] the subsequent establishment of the phase coherence of the fluctuating Cooper pairs at $T < T_c$ [17].

5. CONCLUSION

The investigation of the effect of partial substitution of Y by Cd on the mechanism of excess conductivity in Y-Ba-Cu-O polycrystals showed that partial substitution of Y by Cd leads to a decrease in the critical temperatures of the $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ (Y2) sample compared to $YBa_2Cu_3O_{7-\delta}$ (Y1) (respectively T_c (Y2) = 90.9 K and T_c (Y1) = 92.628K). In this case, the resistivity of the sample $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ in the normal phase at 300K increases (2 times) compared to $YBa_2Cu_3O_{7-\delta}$. At the same time, there is an expansion of the temperature regions of PS and FLP, as well as a decrease in the coherence length of Cooper pairs.

Studies and analysis have shown that the excess conductivity $\Delta\sigma(T)$ in $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ in the

temperature range $T_c < T < T^*$ is satisfactorily described in the framework of the model of local pairs [3,14].

The analysis result of the pseudogap state by the method of excess conductivity confirmed that the model of local pairs in this case is applicable to both samples. At $T \rightarrow T_c$, the behavior of $\Delta\sigma(T)$ of both samples obeys the Aslamazov – Larkin theory for 2D and 3D fluctuations [8, 11]. Thus, before the transition to the superconducting state, the region of superconducting fluctuations is always realized in the form of a PCF, in which $\Delta\sigma(T)$ is described by equation (2) for 3D superconductors (that is, before the SP transition, the HTSC transition is always three-dimensional).

Thus, it can be assumed that in $YBa_2Cu_3O_{7-\delta}$ and $Y_{0.7}Cd_{0.3}Ba_2Cu_3O_{7-\delta}$ PG is formed by converting the d-wave SC of the energy gap in CuO_2 planes into the corresponding gap of the fluctuation Cooper pairs above T_c .

-
- [1] E.B. Amitin, K.R. Jdanov, A.G. Blinov, et al. FNT, 31, 4, 323-326, 2005 (in Russian).
- [2] M.V. Sadvovskiy. UFN, 171, 539-564, 2001 (in Russian).
- [3] M.R. Trunin. UFN, 175, 10, (2005), 1017-1037, 2005 (in Russian).
- [4] A.L. Solovyov, V.M. Dmitriyev. FNT, 32, 6, 753 - 760, 2006 (in Russian).
- [5] A.L. Solovjov, M.A. Tkachenko, R.V. Vovk, A. Chroneos. Fizika C, 501, 24-31, 2014 (in Russian).
- [6] He Rui-Hua, M. Hashimoto, H. Karapetyan et al. Science, 331, 1579 - 1583, 2011.
- [7] A.A. Abrikosov. UFN, 174, 11, 1233-1239, 2004 (in Russian).
- [8] L.G. Aslamazov and A.L. Larkin. Phys. Lett., 26A, 6, 238-239, 1968.
- [9] S.A. Aliev, S.S. Ragimov, V.M. Aliev. Fizika, 2004, 10, 4, 42 - 43, 2004
- [10] V.M. Loktev, V.M. Turkowski. Low temperature physics 30, 3, 247-260, 2004 (in Russian).
- [11] S. Hikami, A.I. Larkin. Modern Phys. Lett, v. B2, 693-697, 1988 (in Russian).
- [12] Oh B., Char K., Kent A.D. et al. Phys. Rev. B 37, 13, 7861 - 7864, 1988.
- [13] A.L. Solovyov, V.M. Dmitriyev. FNT, 35, 3, 227-264, 2009 (in Russian).
- [14] A.A. Kordyuk. FNT, 41, 5, 417 - 444, 2015 (in Russian).
- [15] D.D. Prokofyev, M.P. Volkov, Y.A. Boykov. FTT, 45, 7, 1168-1176, 2003 (in Russian).
- [16] V.V. Florentyev, A.V. Inyushkin, A.N. Taldenkov, et al., Superconductivity: physics, chemistry, technique, 3, 10, v.2, 2302-2319, 1990 (in Russian).
- [17] R. Peters and J. Bauer. Phys. Rev. B 92, 014511– Published 22 July, 2015.

Received: 06.02.2019